

AD-A161 925


CREEP OF THERMOSETTING PLASTICS IN AIR AND IN A
PHYSIOLOGICAL SOLUTION(U) FOREIGN TECHNOLOGY DIV
WRIGHT-PATTERSON AFB OH G I ROYTBURG ET AL. 01 NOV 85
FTD-ID(RS)T-0167-05 F/G 20/11

1/1

UNCLASSIFIED

NL



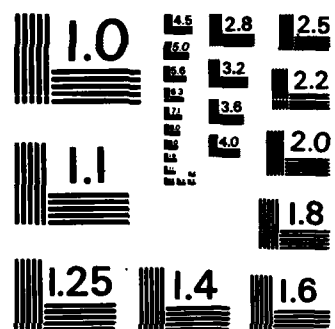


MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

2

FTD-ID(RS)T-0167-85

AD-A161 925


FOREIGN TECHNOLOGY DIVISION

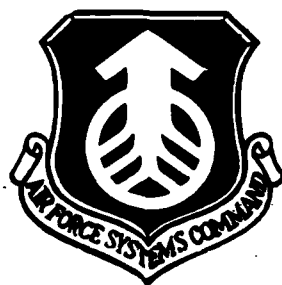

CREEP OF THERMOSETTING PLASTICS IN AIR AND IN A
PHYSIOLOGICAL SOLUTION

by

G.I. Roytberg, V.N. Kestel'man, R.Z. Rakhimov

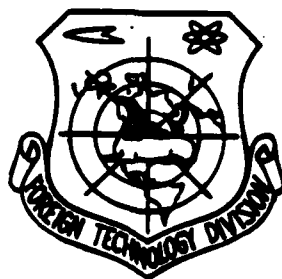

DTIC
ELECTE
DEC 3 1985
S B D

DTIC FILE COPY

Approved for public release;
distribution unlimited.



85 11 29 125

EDITED TRANSLATION

FTD-ID(RS)T-0167-85

1 Nov 85

MICROFICHE NR: FTD-85-C-001027

CREEP OF THERMO SOFTENING PLASTICS IN AIR AND IN A
PHYSIOLOGICAL SOLUTION

By: G.I. Roytberg, V.N. Kestel'man, R.Z. Rakhimov

English pages: 6

Source: Fiziko-Khimicheskaya Mekhanika Materialov,
Nr. 5, 1972, pp. 81-84

Country of origin: USSR

Translated by: Robert D. Hill

Requester: FTD/TQTD

Approved for public release; distribution unlimited.

THIS TRANSLATION IS A RENDITION OF THE ORIGINAL FOREIGN TEXT WITHOUT ANY ANALYTICAL OR EDITORIAL COMMENT. STATEMENTS OR THEORIES ADVOCATED OR IMPLIED ARE THOSE OF THE SOURCE AND DO NOT NECESSARILY REFLECT THE POSITION OR OPINION OF THE FOREIGN TECHNOLOGY DIVISION.

PREPARED BY:

TRANSLATION DIVISION
FOREIGN TECHNOLOGY DIVISION
WP-AFB, OHIO.

U. S. BOARD ON GEOGRAPHIC NAMES TRANSLITERATION SYSTEM

Block	Italic	Transliteration	Block	Italic	Transliteration
А а	<i>А а</i>	A, a	Р р	<i>Р р</i>	R, r
Б б	<i>Б б</i>	B, b	С с	<i>С с</i>	S, s
В в	<i>В в</i>	V, v	Т т	<i>Т т</i>	T, t
Г г	<i>Г г</i>	G, g	У у	<i>У у</i>	U, u
Д д	<i>Д д</i>	D, d	Ф ф	<i>Ф ф</i>	F, f
Е е	<i>Е е</i>	Ye, ye; E, e*	Х х	<i>Х х</i>	Kh, kh
Ж ж	<i>Ж ж</i>	Zh, zh	Ц ц	<i>Ц ц</i>	Ts, ts
З з	<i>З з</i>	Z, z	Ч ч	<i>Ч ч</i>	Ch, ch
И и	<i>И и</i>	I, i	Ш ш	<i>Ш ш</i>	Sh, sh
Й й	<i>Й й</i>	Y, y	Щ щ	<i>Щ щ</i>	Shch, shch
К к	<i>К к</i>	K, k	Ъ ъ	<i>Ъ ъ</i>	"
Л л	<i>Л л</i>	L, l	Ы ы	<i>Ы ы</i>	Y, y
М м	<i>М м</i>	M, m	Ь ь	<i>Ь ь</i>	'
Н н	<i>Н н</i>	N, n	Э э	<i>Э э</i>	E, e
О о	<i>О о</i>	O, o	Ю ю	<i>Ю ю</i>	Yu, yu
П п	<i>П п</i>	P, p	Я я	<i>Я я</i>	Ya, ya

*ye initially, after vowels, and after ъ, ь; e elsewhere.
When written as ё in Russian, transliterate as yě or ě.

RUSSIAN AND ENGLISH TRIGONOMETRIC FUNCTIONS

Russian	English	Russian	English	Russian	English
sin	sin	sh	sinh	arc sh	sinh ⁻¹
cos	cos	ch	cosh	arc ch	cosh ⁻¹
tg	tan	th	tanh	arc th	tanh ⁻¹
ctg	cot	cth	coth	arc cth	coth ⁻¹
sec	sec	sch	sech	arc sch	sech ⁻¹
cosec	csc	csch	csch	arc csch	csch ⁻¹

Russian	English
rot	curl
lg	log

GRAPHICS DISCLAIMER

All figures, graphics, tables, equations, etc. merged into this translation were extracted from the best quality copy available.

CREEP OF THERMO-softening PLASTICS IN AIR AND IN A PHYSIOLOGICAL SOLUTION

G.I. Roytberg, V.N. Kestel'man, R.Z. Rakhimov
(Moscow Technological Institute of the Food Industry)

The creep of polymer materials is studied predominantly under conditions of static uniaxial tension [1-4]. Established at present is the existence of elastic, elasto-elastic (nonstationary) and viscous (stationary) components of total creep strain. The total strain at a constant tensile load and temperature and also the duration of the loading are connected with each other, [2]:

$$\epsilon_n = \epsilon_y + \epsilon_{ye}(\sigma) + v_r(\sigma)t, \quad (1)$$

where ϵ_n is the total creep strain; ϵ_y - elastic component; ϵ_{ye} - elasto-elastic (relaxation) deformation; $v_r t$ - viscous deformation (v_r - rate of viscous deformation, t - time). Liquid media under these conditions do not change the shape of the creep curves. It was of interest to clarify the possibility of using equation (1) for describing the creep of structural thermosoftening plastics with other forms of the stressed state in air and in liquid media.

We studied the creep of polymers under normal conditions in air and in the model medium - the physiological solution (0.9% solution of NaCl in distilled water) under static bending and compression. The objects of the investigation were polyamide-12 (P-12), the copolymer of trioxane with dioxalane (STD), fluorinated polymethylmethacrylate (PMMAF), and casting polyethylene terephthalate (PETF). The standard bars (for bending with a dimension of 10X15X120 mm, for a compression of 10X10X15 mm) were made by the casting method under pressure (P-12, STD, PETF) and machining from a block (PMMAF). Tests were conducted under stresses σ , which comprise different portions of the short-term breaking load σ_{kp} for each material. The

Received Russian Foreign Technology, Translation, USSR;

short-term bending strength of the thermosoftening plastics was determined at a rate of 50 mm/min and for compression and tension - at a rate of 15 mm/min (Table 1). Creep strain was estimated with a precision of up to 0.01 mm according to results of not less than five experiments.

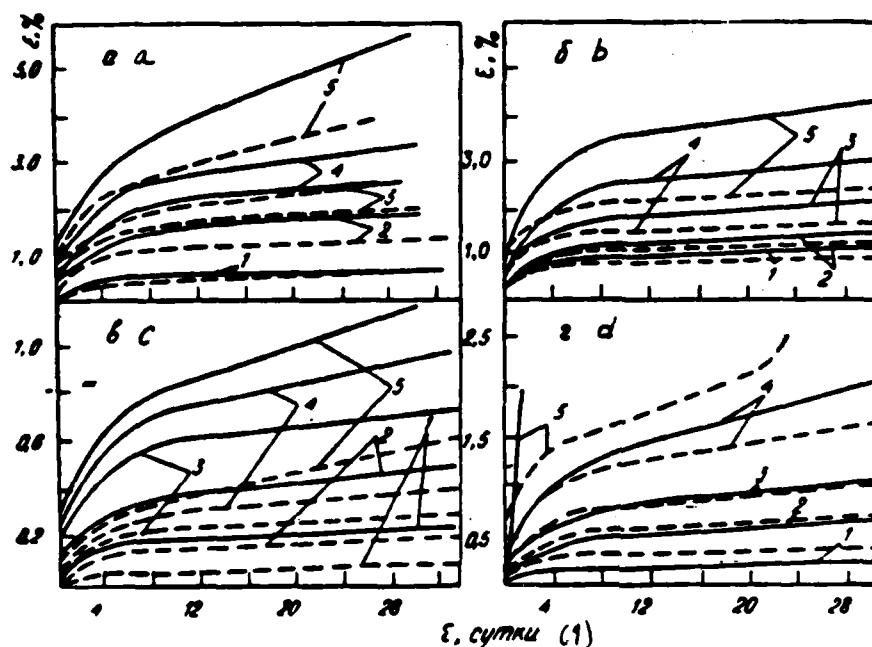


Fig. 1. Creep of P-12^(a), STD (b), PETF (c), and PMMAF (d) in air (dashed lines) and in a physiological solution (solid lines) in the compression process at different values of σ/σ_{kp} : 1 - 0.05; 2 - 0.1; 3 - 0.2; 4 - 0.3; 5 - 0.4. Key: (1) days.

As is evident from Fig. 1, all the obtained creep curves consist of two main sections: nonstationary and stationary creep strains (the instantaneous elastic strain is not reflected on the figures). These curves concur in shape with the known creep curves under conditions of static tension of the majority of the solid polymer materials. Under static bending the picture was similar. In the physiological solution the intensity of the creep strains is different than it is with tests in air, but the nature of the curves remains unchanged.

Usually, it is accepted to consider that in the region of the stationary strain, when the rate of the process is constant, a viscous

deformation is observed, and in the region of the nonstationary strain, an elasto-elastic deformation is observed. To separate the elasto-elastic deformation, individual investigators [5] continued the linear segment of the curve in coordinates $\epsilon_n - \tau$ to the intersection with the ordinate ϵ_n , thereby disregarding the time to the approach of the maximum of the nonstationary creep strain. But under the conditions accepted by us, the time of the deformation of the nonstationary creep is very significant with respect to the total time of action of the load, and, therefore, we cannot disregard it.

Table 1

Short-term strength of thermosoftening plastics (kg/cm^2)

(1) Материал	(2) При растя- жении	(3) При сжатии	(4) При изгибе
П-12	112	508	780
СТД	659	890	1000
ПММАФ	800	1333	1350
ПЭТФ	180	1040	552

Key: (1) Material; (2) Under tension; (3) Under compression; (4) Under bending.

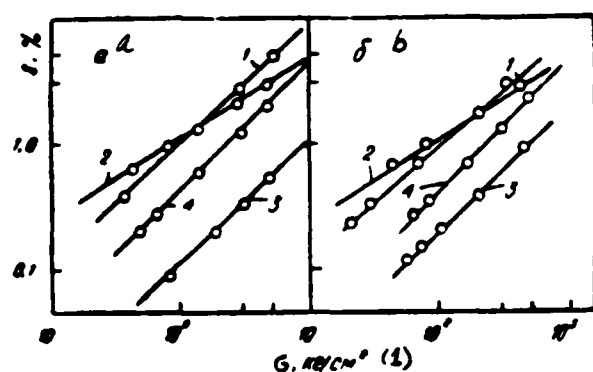


Fig. 2. Dependence of the maximum of nonstationary creep P-12 (1), STD (2), PETF (3), and PMMAF (4) in air (a) and a physiological solution (b) on stress σ under compression. Key: (1) kg/cm^2 .

In logarithmic coordinates Fig. 2 gives the dependence of the magnitude of the elasto-elastic strain on stress σ under compression in air and a model medium. The rectilinearity of the graphs confirms the earlier proposed exponential function between the strain and stress [5]:

$$\epsilon_{el} = A\sigma^b, \quad (2)$$

where A is the parameter dependent on the medium; k - the coefficient determined by the form of loading (Table 2). Straight lines of the nonstationary creep in a physiological solution are located somewhat higher than the similar curves obtained during the test in air.

Table 2

Values of parameters for the creep equation for thermosoftening plastic P-12

(1) Вид деформирования	(2) Напряжение, кг/см ²	(3) Время до наступления предела неустойчивости деформации, сутки		(6) Константы				$\dot{\epsilon}_T$	
				A		k			
		(4) Воздух	(5) Физ. раствор	(4) Воздух	(5) Физ. раствор	(4) Воздух*	(5) Физ. раствор*		
Изгиб (7)	39	2	3	3,2·10 ⁻²	4,07·10 ⁻²	1,0	1,0	0,0100	0,0154
	78	3	5					0,0230	0,0416
	156	5	7					0,0454	0,0578
	234	4	11					0,0833	0,0920
	312	8	9					0,1010	0,1820
	390	10	9					0,1430	0,2040
Сжатие (8)	20,8	4	7	2,46·10 ⁻²	3,02·10 ⁻²	0,85	0,85	0,000667	0,000667
	50,6	10	12					0,000667	0,001270
	110,2	11	11					0,001200	0,001660
	178,8	10	10					0,002600	0,003300
	238,4	8	10					0,00647	0,01000

(4) * Размерность $\dot{\epsilon}_T$ при изгибе мм/сутки, при сжатии 1/сутки.

Key: (1) Form of deformation; (2) Stress, kg/cm²; (3) Time to approach of maximum of nonstationary deformation, days; (4) Air; (5) Physiol. solution; (6) Constants; (7) Bending; (8) Compression; (9) *Dimensionality $\dot{\epsilon}_T$ with bending - mm/days and with compression - 1/days.

In considering the dependence (2) and also the time to the approach of the maximum of the nonstationary deformation of creep, we can present equation (1) in the following form:

$$\epsilon_{\sigma} = \epsilon_{\sigma 0} + A \sigma^k + v_{T(0)} (1 - t_{1(\sigma)}). \quad (3)$$

where $t_{1(\sigma)}$ is the time during which the maximum of the nonstationary strain is achieved. The deviation of values of creep strain, obtained according to relation (3), from the experimental values for the P-12 was more than 6%, for the STD - 8%, the PMMAF - 6%, and PETF - 9%.

In formula (3) the rate of the stationary creep strain $\dot{\epsilon}_T$ and the time of achievement of the maximum of nonstationary strain t_1

are also a stress function. In conditions of our experiment, it is impossible to disregard the time t_1 due to the comparatively short total time of the test. Considering this, we made an attempt mathematically to describe the dependence of the deformation of the stationary creep on stress. It was found that for thermosoftening plastics P-12 and STD undergoing static bending, the dependences $v(\sigma)$ and $t_1(\sigma)$ in air and in a model medium are linear in logarithmic coordinates (Figs. 3 and 4) and, consequently, are described by the exponential function:

$$v = B\sigma^m \quad (4)$$

and

$$t_1 = C\sigma^n, \quad (5)$$

where B , C , m , and n are constants. For the STD with bending in a model medium, the linearity is retained to $\sigma = 200 \text{ kg/cm}^2$.

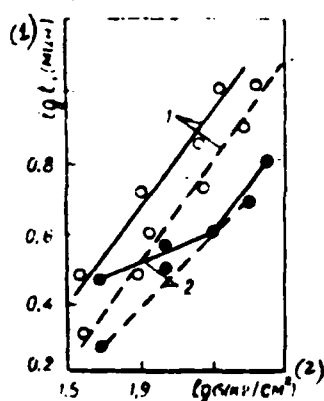


Fig. 3.

Fig. 3. Dependence of the rate of stationary creep strain on stress σ with static bending of P-12 (1) and STD (2) in air (dashed curves) and in model medium (solid lines). Key: (1) min; (2) kg/cm^2 .

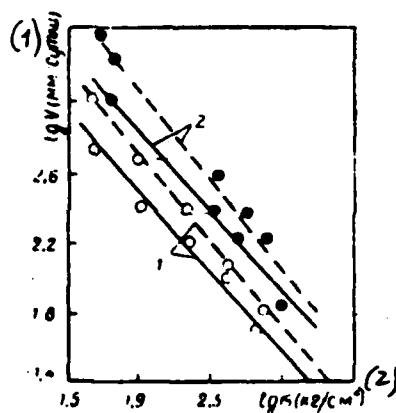


Fig. 4.

Fig. 4. Dependence of time of achievement of maximum of nonstationary creep strain on stress σ with static bending of P-12 (1) and STD (2) in air (dashed line) and in model medium (solid lines). Key: (1) mm/days; (2) kg/cm^2 .

Thus for thermosoftening plastics with a high degree of crystallinity (P-12 and STD), the creep in the process of static bending at high stresses in air and in a physiological solution can be described by the following equation:

$$\epsilon_{\text{st}} = \frac{\sigma}{E} + A\sigma^2 + B\sigma^m(1 - C\sigma^n). \quad (6)$$

References

1. A.H. Stuart. Physics of High Polymers, Springer-Verlag, Berlin, 1956.
2. W. Holzmuller, K. Altenburg. Physics of Plastics, Akademie-Verlag, Berlin, 1961.
3. J. Marin. Appl. Mech. Rev., 1951, 4, 683.
4. W. Findley. Appl. Mech. Rev., 1953, 6, 49.
5. H.A. Bokshitskaya. Khimicheskoye mashinostroyeniye [Chemical Machine Building], 1963, No. 2.

Received 15 July 1971



Accession For	
NTIS	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	

END

FILMED

1-86

DTIC